




**STANNOL**

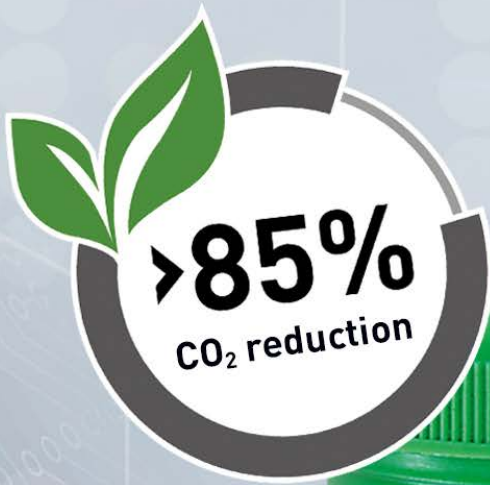

# SP6000

## FACTBOOK

# Table of content

<b>Introduction</b>	03
<b>Test results at a glance</b>	04
<b>SP6000 in comparison</b>	04
<b>Instructions for use</b>	06
<b>Tests</b>	07
SIR Test	07
Solderball Test	08
Wetting Test	08
Slump Test	09
Copper Corrosion	09
Copper Mirror Test	10
Acid Value	10
Halide Evaluation	10
Printability (Benchmark II)	11
Printing After Wait (PAW) (Benchmark II)	11
<b>Delivery forms</b>	12





## Introduction

Stannol solder paste SP6000 has been specially developed for use with the alloys TSC305 (Sn96.5Ag3Cu0.5) T4 and TSC105 (Sn98.5Ag1Cu0.5) T4.

During the development of SP6000, we placed a special focus on environmental compatibility in addition to the technical properties.

### **More than 85 percent CO<sub>2</sub> savings**

The result: An impressive reduction of CO<sub>2</sub> emissions by more than 85 percent compared to common solder pastes, for example through the use of recycled solder, sustainable packaging materials and climate-neutral transport. With SP6000, we are not only focusing on performance, but also on sustainability.


### **Larger stencil thickness and step stencils**

Another goal was to realise a solder paste in particle size 4 that could be used for a 120-/125-µm stencil as well as for a step stencil with 150 µm. The challenge was to avoid solder balls on passive components (mid-chip balling). The cause of solder balls is the capillary action between the components and the PCB. A larger stencil thickness and fine solder powder promote this phenomenon. Good compatibility with step stencils was also taken into account during development.

## Test results at a glance

Tests	Specification	Result
Copper corrosion:	ANSI/J-STD-004C – IPC-TM-650, Method 2.6.15	pass
Copper mirror:	ANSI/J-STD-004C – PC-TM-650, Method 2.3.32	pass
Surface insulation resistance:	ANSI/J-STD-004C – IPC TM650, Method 2.6.3.3/2.6.3.7	pass
Silver chromate paper test:	ANSI/J-STD-004C – IPC-TM-650, Method 2.3.33	pass
Chlorides:	ANSI/J-STD-004C – IPC-TM-650, Method 2.3.35	no addition
Bromides:	ANSI/J-STD-004C – IPC-TM-650, Method 2.3.35	no addition
Solder balling:	ANSI/J-STD-005A – IPC TM-650, Method 2.4.43 after 1 h at room temperature after 24 h at room temperature	pass, class 1 pass, class 1
Wetting test:	ANSI/J-STD-005A – IPC TM-650 Method 2.4.45	pass, class 1
Slump test: (T4, stencil 150 µm)	10 minutes at 150 °C	pass, 0,3 mm
Open time:	laboratory internal specification	at least 8 h at 23 °C/65 % rF
Flux activity classification:	J-STD-004	RELO

## SP6000 in comparison

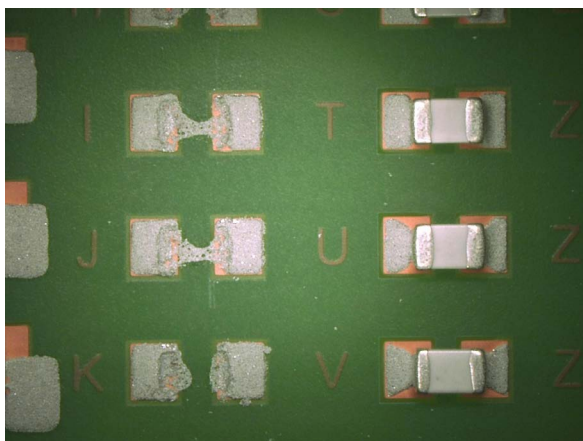

*Solder paste misprint*




*Stannol solder paste SP6000*

### AOI compatibility




The flux residues of SP6000 are clear and transparent after soldering – this prevents the detection of pseudo defects during automatic optical inspection (AOI).

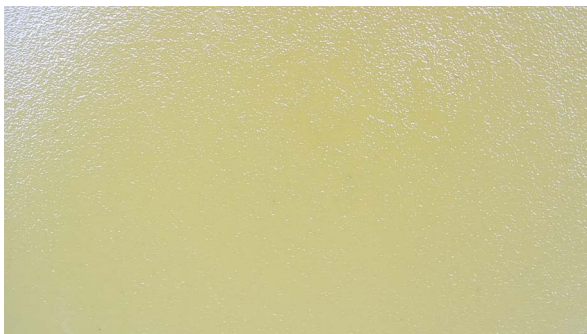

The flux residues of a conventional solder paste are yellowish after soldering.

### High stability


Due to the high stability, a very wide process window for solder paste printing is achieved.

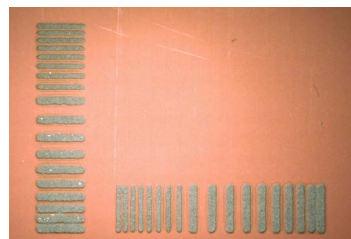

### Voiding




*Void formation with conventional solder paste*



*Reduced void formation with SP6000*



## Solder profile

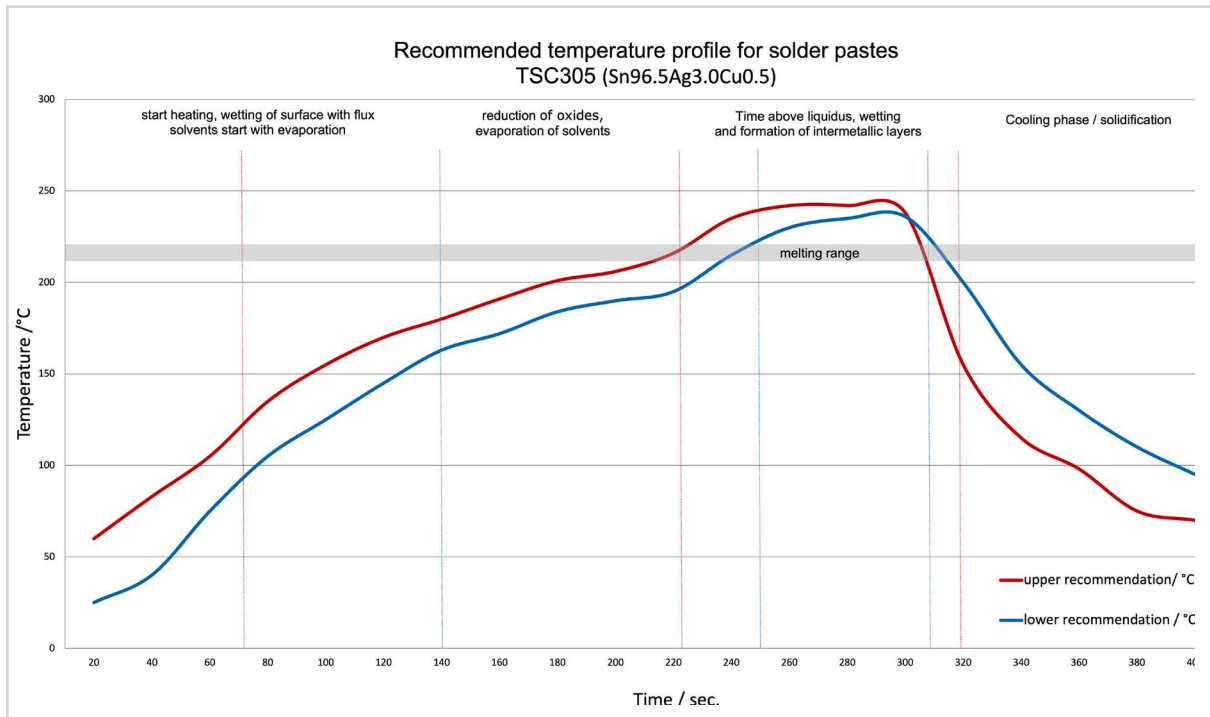

## Instructions for use

### Cleaning

SP6000 is classified as L0 solder paste and is therefore considered a typical No-Clean product. If cleaning is still required, approved products from Zestron or Kolb Cleaning can be used.

### Transport and storage

SP6000 should be transported in packaging in which the temperature of 0 to 8 °C can be kept constant for

as long as possible. Transport time should be kept to a minimum. Transport temperatures above 40 °C should be avoided if possible. A supply chain profile can be created with the help of a thermologger. Storage at 0 to 8 °C increases the duration of use. The solder paste SP6000 has a minimum shelf life of six months under the described storage conditions.

### Flux classification according to J-STD-004C

The tests described in the standard are used to test and categorise fluxes for their properties under standardised conditions. Depending on the test results, the fluxes are classified into the categories L, M and H. The number after the test indicates whether the flux is halogen-free or not. The number following the category indicates whether the flux contains halides (1) or is halide-free (0). If all tests are passed in the uncleaned condition, we speak of No-Clean products. However,

this designation only states that the corresponding products have passed the tests in the uncleaned state. The test conditions do not cover all extreme conditions that a PCB may experience in the field. The final risk assessment of the residues and the associated decision as to whether the flux residues have to be removed after the soldering process are in any case the responsibility of the respective electronics manufacturer.

# Tests

## SIR Test (IPC-TM-650, Method 2.6.3.3/2.6.3.7)

### Introduction

The abbreviation SIR stands for Surface Insulation Resistance. In a SIR test, the SIR values of a live PCB are recorded over time under defined environmental conditions and a defined PCB geometry. A drop in the SIR value in the course of the measurement indicates unwanted reactions, e.g. flux residues.

### Test conditions

**Test boards:** 400-200  $\mu\text{m}$  comb pattern

**Bare copper on FR-4:**  $40 \pm 1 \text{ }^\circ\text{C}$ ,  $90 \pm 3 \text{ \% rH}$

**Measuring range:** up to  $10^{13} \Omega$  with electrical preload  
5 VDC


**Test duration:** 168 h (7 days)

### Test criteria

Criteria for passing the SIR test

- All SIR measurements shall achieve a minimum resistance of  $100 \text{ M}\Omega$  on all test samples after 168 hours.
- There shall be no evidence of electrochemical migration (filament growth) that reduces the conductor spacing by more than 20 percent.
- There shall be no corrosion of the conductors (minor discolouration is acceptable).

### Test results

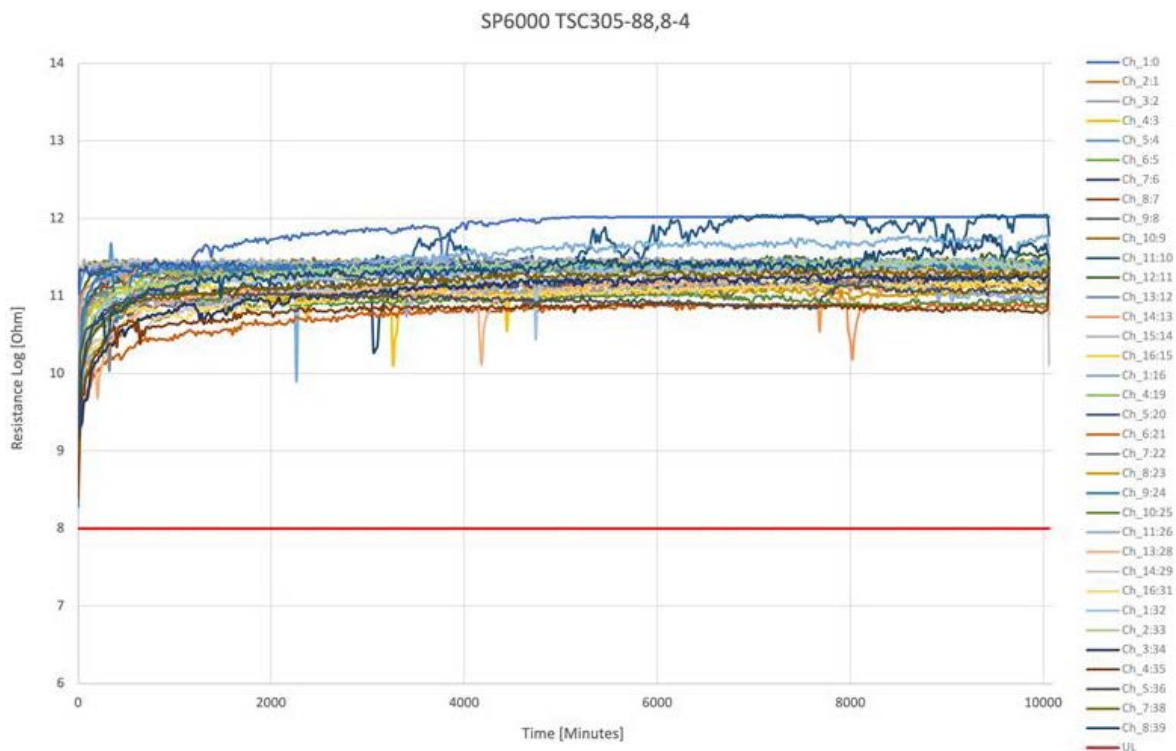

After 168 h  $>108 \Omega$  = pass

## Solderball Test (IPC-TM-650, Method 2.4.43)

### Introduction

The solder ball test is used to assess the quality of the solder paste. For this purpose, defined quantities of solder paste are applied to a ceramic plate using a stencil and melted with the help of a heat source.

### Test conditions

**Ceramic plate:** 50 x 50 x 0,6 mm (Al<sub>2</sub>O<sub>3</sub>-98 %)

**Stencil:** 150 µm

**Temperature:** 150 °C and 250 °C

**Test duration:** 20 sec and 30 sec

### Test results



**One single fully formed solder ball = pass**

## Wetting Test (IPC-TM-650, Method 2.4.45)

### Introduction

The wetting test is used to assess the activity of the solder paste. For this purpose, defined quantities of solder paste are applied to a copper plate using a stencil and melted using a heat source.

### Test conditions

**Copper plates:** 50 x 50 x 0,8 mm CU sheet ETP

**Stencil:** 150 µm

**Temperature:** 150 °C and 250 °C

**Test duration:** 20 sec and 30 sec

### Test results



**The surface is completely wetted = pass**



## Slump Test

### Introduction

The Slump Test helps to assess the stability of the solder paste. For this purpose, defined quantities of solder paste are applied to a substrate using a stencil and dried in a thermal oven.


### Test conditions

**Substrate:** 50 x 50 x 0,8 mm

**Temperature:** 150 +/-5 °C

**Test duration:** 10 – 15 min

### Test results

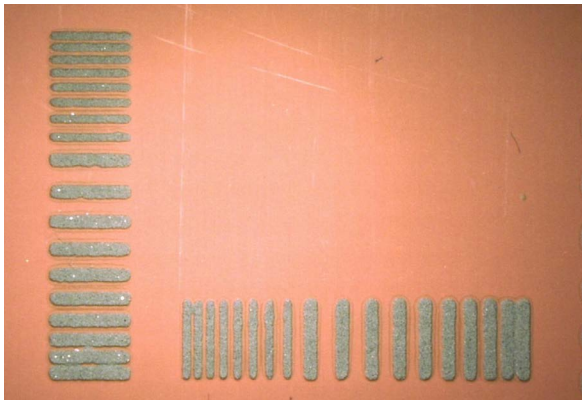

*Contour stability 0,3*

## Copper Corrosion (IPC-TM-650, Method 2.6.15)

### Introduction

The copper corrosion test is used to determine the corrosive properties of flux residues under defined surrounding conditions.

### Test conditions

**Test coupon:** 50 x 50 x 0,5 mm copper

**Climate:** 40 ± 1°C, 93 ± 2 % rH

**Test duration:** 240 h (10 days)

### Test criteria

**Low/No Corrosion (L):** No signs of corrosion are observed. The initial colour change that may develop when the copper coupon is heated during soldering is not considered.

**Moderate Corrosion (M):** Slight white or coloured spots in the flux residues but without pitting of the copper

**High Corrosion (H):** Development of green-blue discoloration and/or corrosion with observation of pitting of the copper surface.

### Test results



*No corrosion: Classification L*

## Copper Mirror (IPC-TM-650, Method 2.3.32)

### Introduction

The copper mirror test has been developed to determine the removal effect that the flux has on the copper layer.

### Test conditions

**Test coupon:** Glas panel with a thickness of approximately 50nm

**Climate:**  $23 \pm 2^\circ\text{C}$ ,  $50 \pm 5\%$  rH

**Test duration:** 24 h (1 day)

### Test criteria

**L =** The copper layer was not completely removed.

No breakthrough of the copper layer

**M =** Complete removal of copper on a maximum of 50 percent of the surface of the applied solution (breakthrough smaller than 50 percent).

**H =** Complete removal of the copper layer on more than 50 percent of the wetted area (breakthrough greater than 50 percent).

### Test results



*No breakthrough = pass (Classification L)*

## Acid value (IPC-TM-650, Method 2.3.13)

### Introduction

The acid value measures the content of acidic, active substances in a sample. The acid value is measured by the amount of potassium hydroxide (KOH) in milligrams needed to neutralise one gram of the substance.

### Test criteria

The method is described in IPC-TM-650, method 2.3.13. Method B is used.

### Test results

182 mg KOH/g

## Halide evidence (IPC-TM-650, Method 2.3.35)

### Introduction

The halide test is used for the detection of chloride and bromide ions in liquid or extracted fluxes.

### Test criteria

The method is described in IPC-TM-650, method 2.3.35.

### Test results

No halides can be detected.

## Printability (Benchmark II)

### Introduction

Good printability is important to achieve a good line resolution for consistent results with different printing parameters.

### Printer settings

Speed: 50 mm/s


Separation speed: 10 mm/s

Squeegee pressure: 0.25 kg/cm


Stencil thickness: 120  $\mu\text{m}$

### Test results

Printability (Benchmark II):

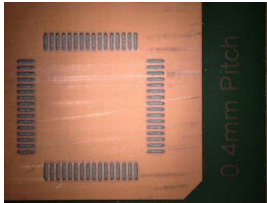

0,4 mm Pitch

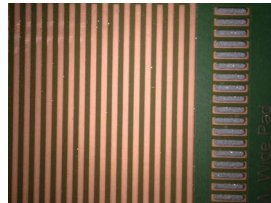

100P BQFT  
(horizontal narrow)

## Printing After Wait (Benchmark II)

### Introduction

Printing After Wait (PAW) is important for restoring the same print quality immediately after production line downtimes.

### Printer settings

Speed: 50 mm/s

Separation speed: 10 mm/s


Squeegee pressure: 0.25 kg/cm

Stencil thickness: 120  $\mu\text{m}$

### Test results




Print after 1 hour wait  
(180  $\mu\text{m}$ )

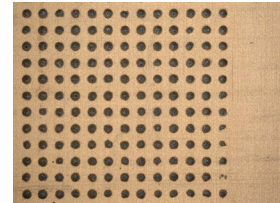

Print after 1 hour wait



100P BQFT  
(horizontal narrow)

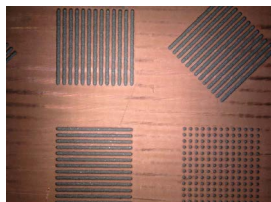

Print after stencil  
cleaning

# Delivery forms

Titel	Alloy	Packaging	Weight
SP6000	TSC305 T4	Jar or cartridge	500–1200 g
SP6000D	TSC305 T3	Dispenser	40–125 g

Further articles are available on request.

For more technical information,  
please visit the Stannol website at  
[www.stannol.de/en/downloads](http://www.stannol.de/en/downloads)



# STANNOL

## greenconnect

responsible soldering products

Under the name greenconnect  
Stannol offers a complete product  
range that focuses on sustainability  
and fairness – for a greener future!



SOLDER WIRE



FLUX



SOLDER PASTE



ACCESSORIES



SOLDER BARS



# STANNOL

Stannol GmbH & Co. KG  
Haberstr. 24, 42551 Velbert, Germany  
Tel: +49 (0) 2051 3120 -0  
info@stannol.de  
[www.stannol.de](http://www.stannol.de)

